

SP0153799
FINAL REPORT

Multi Element Package



DND Mining

COPIES TO : Del Schoening CLIENT REFERENCE No: Sulfide Ore Head Material RECEIVED : 5-May-2025
: dndranchnvbranch@cccomm.net No. SAMPLES : 4 REPORTED : 22-May-2025
: MAIN SAMPLE TYPE : All Laboratory Analysis were performed
: between the above Received and Reported dates

COMPANY DISCLAIMER :-

When small samples are submitted, AAL may process the sample at smaller than specified weights to retain some pulp for quality control reassay.
When Values exceed upper limits, AAL will run an Over Range analysis, to establish an accurate value. Additional cost will apply.
Due to USDA Soil Quarantine programs - all foreign and some domestic soil material must be decontaminated by drying @ 125c for 48 hours, which will result in loss of Mercury (Hg).

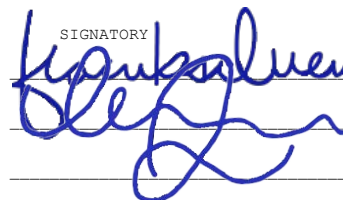
NEVADA LEGISLATIVE DISCLAIMER :-

The results of this assay were based solely upon the content of the sample submitted. Any decision to invest should be made only after the potential investment value of the claim or deposit has been determined based on the results of assays of multiple samples of geological materials collected by the prospective investor or by a qualified person selected by him and based on an evaluation of all engineering data which is available concerning any proposed project. Nevada State Law NRS 519.130.

ANALYSIS	Wt	Au	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Dy	Er	Eu	Fe	Ga	Gd	Ge	Hf	Hg	Ho	In
METHOD	WEIGHDry	FAAu30	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61
UNIT	Kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
LOWER LIMIT	0.01	0.003	0.05	300	0.5	2	0.02	0.02	300	0.02	0.2	0.2	0.2	0.2	0.5	0.05	0.05	0.05	300	5	0.05	0.02	0.03	0.01	0.05	0.008

ANALYSIS	K	La	Li	Lu	Mg	Mn	Mo	Na	Nb	Nd	Ni	P	Pb	Pr	Rb	Re	S	Sb	Sc	Se	Sm	Sn	Sr	Ta	Tb	Te
METHOD	IM-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61
UNIT	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
LOWER LIMIT	100	0.1	2	0.05	5	5	0.2	100	0.03	0.05	0.5	20	3	0.05	0.8	0.003	30	0.05	0.05	0.05	0.05	0.05	5	0.03	0.2	0.03

ANALYSIS	Th	Ti	Tl	Tm	U	V	W	Y	Yb	Zn	Zr
METHOD	IM-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61	I-4AB61
UNIT	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
LOWER LIMIT	0.08	30	0.008	0.05	0.05	3	0.07	0.05	0.05	3	0.3

SIGNATORY

ANALYSIS
FA
ICP

SP0153799
FINAL REPORT

	<u>Abbreviation</u>	<u>Definition</u>
Preparation	DIP	Sample Destroyed in Preparation
	DIS	Sample Destroyed in Shipment
	ISS	Insufficient Sample Submitted
	SDI	Sample Diesel Impregnated
	SHI	Sample Hydraulic Impregnated
	SNR	Sample Not Received
Analysis	STD - ??	International Reference Material Standard
	STD - AAL##	AAL generated standard material
	BLANK	AAL Laboratory Silica Blank
	DTF	Data to Follow
	DL	Detection Limit of Method
	< or -	Less Than Lower Detection Limit of Method
	>	Greater than Upper Limit of Method
	N/A	Not Analyzed
	NR	Not Reported
	(R) column	Laboratory repeat weigh, digestion, analysis from original pulp or reject resplit
	D or -D after Sample ID	Client submitted duplicate rig split sample
	-R after Sample ID	Repeat analysis from original pulp reweigh, digestion and analysis
	-X after Sample ID	Repeat analysis from reject resplit, preparation, weigh, digestion and analysis
	ppb	Parts per Billion 0.001 ppm = 1 ppb
	ppm	Parts per Million 1 ppm = 1 mg/Kg
	OPT	Troy Ounces per Short Ton(2,000 lbs)(1 ppm= 0.02917 OPT)
	Oz	Troy Ounce = 31.103 grams
	%	Percent 1%=10,000 ppm
	g	Grams 1g=0.001 kilogram
	mg	Milligrams 1mg=0.001grams
	Kg	Kilograms 1Kg=1000grams
	lbs	Pounds 1lb=0.454kilogram
Method	FA-PB##	Fire Assay Lead Collection - ## sample weight in grams
	GRAV	Gravimetric (Weighed) finish
	SF	Screen Fire Assay reporting a plus, 2 minus fractions and a head Calc
	+ ###	Plus Fraction (Retained on top of Mesh) ###Screen Size
	- ###	Minus Fraction (Passed through Mesh) ###Screen Size
	CN	Cyanide Extraction
	ORE GRADE	2g sample made to 1000ml volumetric for results > upper limit of method
	Ox-H2SO4 or -HCl	Dilute acid leach for oxide fraction in copper or molybdenum analysis
	QLA	Dilute 10%H2SO4/0.5%Fe2(SO4)3 30C leach for acid soluble copper
	QLT	Dilute 15%H2SO4 30C leach for acid soluble copper
	SAP	Dilute 5%H2SO4/0.5%Fe2(SO4)3 85C leach for acid soluble & chalcocite copper
	D#A	Digestion #=2,3 or 4 Acids 2A=HCl/HNO3 3A=HCl/HNO3/HClO4 4A=HCl/HNO3/HF/HClO4
	HCl	Hydrochloric Acid(37%w/v) Boiling Point 109C
	HF	Hydrofluoric Acid(48%w/v) Boiling Point 108C Extreme Health Hazard
	HClO4	Perchloric Acid(69%w/v) Boiling Point 203C Extreme Fire/Explosion Hazard
	HNO3	Nitric Acid(69%w/v) Boiling Point 121C
	H2SO4	Sulfuric Acid(98% w/v) Boiling Point 338C
	ICP-xB or -xZ	ICP-AES and/or ICP-MS analysis using x=2, 3 or 4 acid digestion
	LiBO2-C	Lithium Metaborate fusion in Carbon crucible
	Na2O2-C	Sodium Peroxide fusion in Carbon crucible
	Na2O2-Zr	Sodium Peroxide fusion in Zirconium crucible
Technique	AAS	Atomic Absorption Spectroscopy
	ICP-AES	Inductively Coupled Plasma Atomic Emission Spectroscopy
	ICP-MS	Inductively Coupled Plasma Mass Spectroscopy
	RG	Research Grade (Low detection limit ICP-AES)
	UT	Ultra Trace (ICP-AES+ICP-MS analyses)
	XRF-ED or -WD	X-Ray Fluorescence (-ED = Energy Dispersive) (-WD = Wavelength Dispersive)
	XRD	X-Ray Diffraction
	ELTRA-I	Carbon & Sulfur infrared detection analyzer inductive heating
	ELTRA-R	Carbon, Hydrogen & Sulfur infrared detection analyzer resistance furnace
	LECO-I	Nitrogen & Oxygen infra red detection analyzer inductive heating
	MW	Microwave Digestion (-PT is at 1500psig and 300C)
	SG-WD or -HP	Specific Gravity-WD=Water Displacement -HP=Helium Pycnometer 1g/cm3=62.4lbs/ft3

SP0153799

FINAL REPORT

CLIENT : DND Mining
PROJECT : BKM
REFERENCE : Sulfide Ore Head Material
REPORTED : 22-May-2025

SAMPLES	Wt	Au	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Dy
	WEIGHDry IO-FAAu30 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61 IM-4AB61															
	0.01	0.003	0.05	300	0.5	2	0.02	0.02	300	0.02	0.2	0.2	0.2	0.2	0.5	0.05
	Kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
Sulfide Ore Head Materi	0.45	4.140	18.22	12878	61.2	1133	1.10	0.10	40544	1.97	2.1	6.2	257.8	3.6	63.8	0.59
BLANK		-0.003	-0.05	3052	0.8	9	0.06	-0.02	319	-0.02	7.4	-0.2	2.9	-0.2	-0.5	0.18
Sulfide Ore Head Material-X		4.310	19.76	12204	58.0	1090	1.05	0.10	38915	1.80	2.0	6.0	245.2	3.4	59.0	0.54
STD - CDN-CM-47		1.220														
STD - OREAS 906			0.85	71072	23.8	2823	2.84	11.03	5834	0.45	86.9	25.3	9.4	6.8	3142.5	3.61

SP0153799

FINAL REPORT

CLIENT : DND Mining
PROJECT : BKM
REFERENCE : Sulfide Ore Head Ma
REPORTED : 22-May-2025

SAMPLES	Er	Eu	Fe	Ga	Gd	Ge	Hf	Hg	Ho	In	K	La	Li	Lu	Mg	Mn
	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61
	0.05	0.05	300	5	0.05	0.02	0.03	0.01	0.05	0.008	100	0.1	2	0.05	5	5
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
Sulfide Ore Head Materi	0.32	0.25	14185	-5	0.72	0.04	0.22	0.50	0.11	0.014	6256	2.7	11	-0.05	1465	347
BLANK	0.06	0.11	502	-5	0.49	-0.02	0.08	0.01	-0.05	-0.008	1171	4.2	-2	-0.05	93	-5
Sulfide Ore Head Materi	0.30	0.22	13390	-5	0.66	0.05	0.20	0.47	0.10	0.011	6051	2.6	10	-0.05	1391	338
STD - CDN-CM-47																
STD - OREAS 906	1.15	1.63	55136	28	6.34	0.21	6.66	0.04	0.48	1.274	27647	40.3	19	0.08	2900	388

SP0153799
FINAL REPORT
CLIENT : DND Mining
PROJECT : BKM
REFERENCE : Sulfide Ore Head Ma
REPORTED : 22-May-2025

SAMPLES	Mo	Na	Nb	Nd	Ni	P	Pb	Pr	Rb	Re	S	Sb	Sc	Se	Sm	Sn
	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61
	0.2	100	0.03	0.05	0.5	20	3	0.05	0.8	0.003	30	0.05	0.05	0.05	0.05	0.05
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
Sulfide Ore Head Materi	29.0	218	0.53	2.81	61.8	198	4115	0.62	33.3	-0.003	718	74.61	3.79	5.44	0.70	0.57
BLANK	0.3	105	0.28	4.44	1.0	-20	7	1.06	3.1	-0.003	-30	0.18	0.45	-0.05	0.78	0.16
Sulfide Ore Head Materi	28.2	182	0.46	2.56	58.6	195	3937	0.56	30.4	-0.003	678	69.24	3.63	4.97	0.62	0.51
STD - CDN-CM-47																
STD - OREAS 906	4.8	26379	10.28	41.13	8.2	275	38	10.57	144.3	-0.003	344	4.08	4.44	4.88	7.86	4.35

SP0153799

FINAL REPORT

CLIENT : DND Mining
PROJECT : BKM
REFERENCE : Sulfide Ore Head Ma
REPORTED : 22-May-2025

SAMPLES	Sr	Ta	Tb	Te	Th	Ti	Tl	Tm	U	V	W	Y	Yb	Zn	Zr
	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61	IM-4AB61
	5	0.03	0.2	0.03	0.08	30	0.008	0.05	0.05	3	0.07	0.05	0.05	3	0.3
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
Sulfide Ore Head Materi	119	0.04	-0.2	0.06	0.73	210	0.213	-0.05	1.51	44	2.44	3.61	0.33	266	11.1
BLANK	6	0.14	-0.2	-0.03	1.15	105	0.022	-0.05	0.28	3	-0.07	0.70	-0.05	-3	3.3
Sulfide Ore Head Materi	113	0.06	-0.2	0.03	0.69	197	0.197	-0.05	1.40	42	2.27	3.41	0.30	258	10.8
STD - CDN-CM-47															
STD - OREAS 906	190	0.67	-0.2	0.15	14.23	777	0.711	0.11	4.81	5	2.29	15.46	0.75	169	256.0